

AD-A081 242

NORTHWESTERN UNIV EVANSTON IL DEPT OF CHEMISTRY F/G 7/4
CRYSTAL STRUCTURE AND PROPERTIES OF TETRATHIAFULVALENUM TRIIOD--ETC(U)
DEC 79 R C TEITELBAUM, T J MARKS, C K JOHNSON N00014-77-C-0231

UNCLASSIFIED

TR-9

NL

1 of 1

AU


WFO-1

END

DATE

3-80

DDM

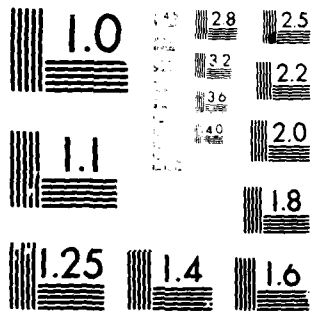

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

ADA081242

W-7405-eng-26

OFFICE OF NAVAL RESEARCH

Contract N00014-77-C-0231

Task No. NR 053-640

TECHNICAL REPORT NO. 9

Crystal Structure and Properties of
Tetrathiafulvalenium Triiodide.

by

Robert C. Teitelbaum, ^{la, b, c} Tobin J. Marks ^{la, 2} and

Carroll K. Johnson ^{Id}

Prepared for Publication

in

The Journal of the American Chemical Society

Northwestern University
Department of Chemistry
Evanston, Illinois 60201

3 December 3, 1979

DTIC
ELECTE
FEB 27 1980

Reproduction in whole or in part is permitted for
any purpose of the United States Government

* This document has been approved for public release and
sale; its distribution is unlimited

* This statement should also appear in Item 10 of Document Control
Data - DD Form 1473. Copies of form available from cognizant
contract administrator.

260805

80

2

23

1/2

unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 9	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Crystal Structure and Properties of Tetrathiafulvalenium Triiodide		5. TYPE OF REPORT & PERIOD COVERED Interim, 1979
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s)		8. CONTRACT OR GRANT NUMBER(s) N00014-77-C-0231
9. PERFORMING ORGANIZATION NAME AND ADDRESS		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR-053-640
11. CONTROLLING OFFICE NAME AND ADDRESS		12. REPORT DATE December 3, 1979
		13. NUMBER OF PAGES 22
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Polyiodide Conductive material Mixed valence material Tetrathiafulvalene TTF Organic conductor		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Slow cooling of a hot acetonitrile solution of tetrathiafulvalene (TTF) and iodine yields a mixture of crystalline products including monoclinic crystals of high iodine composition: $\text{TTF} \cdot \text{I}_3$. A single crystal X-ray structure analysis has been carried out on these crystals of symmetry $P2_1/n$ with 4 molecules per unit cell. The cell parameters are $a = 9.411(2)\text{\AA}$, $b = 18.787(3)\text{\AA}$, $c = 7.771(1)\text{\AA}$, $\beta = 103.2(1)^\circ$, and $V = 1374(1)\text{\AA}^3$. The structure consists of integrated stacks along the $\langle 102 \rangle$ axis with TTF^+ dimers interspersed between pairs		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 68 IS OBSOLETE
S/N 0102-014-6601

unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

of triiodide ions. Consistent with the structural results, single crystal measurements indicate that this material exhibits high electrical resistivity with $\sigma_{RT} < 9 \times 10^{-8} \Omega^{-1} \text{ cm}^{-1}$.

Accession For	
NTIS GRA&I	<input checked="checked" type="checkbox"/>
DDC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	<input type="checkbox"/>
By	
Distribution/	
Availability	
Dist	Available or
A	Special

unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

By acceptance of this article, the publisher or recipient acknowledges the U S Government's right to retain a nonexclusive, royalty-free license in and to any copyright covering the article.

Contribution from the Department of
Chemistry and the Materials
Research Center
Northwestern University
Evanston, Illinois 60201 and
the Chemistry Division
Oak Ridge National Laboratory
Oak Ridge, Tennessee 37830

CRYSTAL STRUCTURE AND PROPERTIES OF
TETRATHIAFULVALENIUM TRIIODIDE

by Robert C. Teitelbaum,^{1a, b, c} Tobin J. Marks^{*1a, 2} and Carroll K. Johnson^{* 1d}

ABSTRACT

Slow cooling of a hot acetonitrile solution of tetrathiafulvalene (TTF) and iodine yields a mixture of crystalline products including monoclinic crystals of high iodine composition: TTF·I₃. A single crystal X-ray structure analysis has been carried out on these crystals of symmetry $P2_1/n$ with 4 molecules per unit cell. The cell parameters are $a = 9.411(2) \text{ \AA}$, $b = 18.787(3) \text{ \AA}$, $c = 7.771(1) \text{ \AA}$, $\beta = 103.2(1)$, and $V = 1374(1) \text{ \AA}^3$. The structure consists of integrated stacks along the

$\langle 102 \rangle$ axis with TTF^+ dimers interspersed between pairs of tri-iodide ions. Consistent with the structural results, single crystal measurements indicate that this material exhibits high electrical resistivity with $\sigma_{\text{RT}} < 9 \times 10^{-9} \Omega^{-1} \text{ cm}^{-1}$.

INTRODUCTION

Considerable attention in recent years has been focused on the chemistry and physics of materials which exhibit highly anisotropic electrical, optical, and magnetic properties.³ Of particular interest have been organic and metal-organic solids which exhibit metal-like charge transport along one crystalline axis. The discovery of the "organic metal" tetrathiafulvalene-tetracyanoquinodimethane, TTF-TCNQ, prompted a number of studies of TTF as an electron donor and precursor for other highly conductive solids. Halogen oxidation, for example, yields a variety of charge transfer salts.⁴

One direction of activity in our Laboratories and others has involved the iodine-containing TTF salts, $\text{TTF} \cdot \text{I}_x$. The stoichiometries prepared to date range from $x=0.71$ to 3.0 , but detailed single crystal characterization has been restricted to a limited number of low iodine phases. The most conductive of these is $\text{TTF} \cdot \text{I}_{0.71}^{4a, b}$ with a room temperature conductivity of ca. $300 \Omega^{-1} \text{ cm}^{-1}$ along the needle axis. This material possesses an ordered, modulated crystal structure containing stacks of eclipsed, partially oxidized TTF^{4b} molecules, and parallel chains of I^- ions.^{4h, 5} Two additional phases of intermediate stoichiometry with $x \sim 2.0$ have been isolated which vary only in the degree of order-disorder. The first $\text{TTF} \cdot \text{I}_2$ structure (space group Immm) contains disordered chains of triiodide ions and disordered TTF stacks $((\text{TTF}^{+0.7})(\text{I}_3^-)_{0.7})^{4g, 6, 7}$. Preliminary X-ray crystallographic investigations sug-

gest that the second $\text{TTF} \cdot \text{I}_2$ phase(space group Fddd) is a superstructure of the first $\text{TTF} \cdot \text{I}_2$ phase with ordered TTF stacks, but again with disordered triiodide ions.^{6, 7} Full expositions of the $\text{TTF} \cdot \text{I}_2$ structures, spectroscopy and transport properties are in preparation. In view of the accumulating knowledge on the above TTF-iodine complexes, it would clearly be of interest to investigate, for comparative purposes, the phase of greatest iodine content. This would provide information on how the crystal structure,⁸ degree of partial oxidation, and transport properties adjust to the increased dopant level. Such information might also shed light on how large amounts of iodine are sometimes accommodated in metal glyoximate⁹ and phthalocyanine¹⁰ lattices. Here, again, phases with very high iodine content have been isolated.^{9, 10} We report here the synthesis, X-ray diffraction structure determination, and single crystal conductivity of the high iodine TTF phase, $\text{TTF} \cdot \text{I}_3$.

EXPERIMENTAL

Synthesis of $\text{TTF} \cdot \text{I}_3$. Tetrathiafulvalene triiodide was prepared under a nitrogen atmosphere by adding dropwise a solution of 80 mg (0.39 mmole) TTF (Aldrich Chemical Co.) in 10 ml acetonitrile (freshly distilled from P_2O_5 under nitrogen), to a stirring solution of 120 mg. (0.47 mmole) triply sublimed I_2 in 10 ml of freshly distilled acetonitrile. Sufficient acetonitrile was added until the total volume was 50 ml. The solution was heated to 50°C with constant stirring until all of the solid present dissolved. Upon slow cooling to room temperature, a mixture of crystals of $\text{TTF} \cdot \text{I}_{0.71}$, $\text{TTF} \cdot \text{I}_2$, and in trace amounts, $\text{TTF} \cdot \text{I}_3$ resulted. The product was then washed with freshly distilled benzene and dried with a stream of nitrogen. The morphology of the $\text{TTF} \cdot \text{I}_3$ crystals are sufficiently different from the other phases to be easily separated by inspection. Insufficient quantities of material were obtained for elemental analysis.

X-ray Diffraction Study. $\text{TTF} \cdot \text{I}_3$ has 4 molecules per unit cell with space group symmetry $\text{P2}_1/\text{n}$. Least-squares refinement of cell parameters using 10 high order reflections gave the unit cell dimension $\underline{a} = 9.411(2)$, $\underline{b} = 18.787(3)$, and $\underline{c} = 7.771(1) \text{ \AA}$, with $\beta = 103.2(1)^\circ$ and $V = 1374(1) \text{ \AA}^3$.

Single crystal intensities from a polyhedral crystal were collected on the Oak Ridge computer-controlled diffractometer using filtered

molybdenum radiation. Of the 3915 unique reflections measured, 3284 had intensities greater than one sigma. A twin or perhaps an unidentified second phase was present and caused at least 75 reflections, mainly in the (hk0) zone, to have excessive observed intensity. The (0k0) reflections were all affected. An absorption correction applied to the data gave transmittancy factors of 0.13 to 0.17.

Structure Solution and Refinement. The three iodine atom positions were found using the direct-methods program MULTAN of Germain, Main and Woolfson.¹¹ These matched the heavy-atom vectors of the Patterson map. The sulfur and carbon atoms were then found using a Fourier map computed with phases based on iodine atom positions. The four hydrogen atoms were placed in idealized positions and their positional parameters included in the refinement.

Refinement of all nonhydrogen atoms with anisotropic thermal motion and hydrogen atom positions led to an R index of 0.078 on F^2 for all 3915 reflections. The refinement was based on 3090 reflections with 75 reflections deleted because of the twinning problem and reflections < 1.5 sigma omitted. The $R(F^2)$ index for the reflections used in the refinement was 0.054. Tables of the final $|F_o|$ and $|F_c|$ values for the 3915 reflections are available upon request.¹²

Atomic scattering factors for S, C, H, and the central I were taken directly from the International Tables of X-ray Crystallography, Volume IV.¹³ Scattering factors for the two outer iodines in the triiodide were taken as the average of the scattering factors for I° and I^{-} , since it has been shown that the negative charge in the triiodide ion is distributed among the outer iodines, while the central iodine is approximately neutral.^{9a, 14} The real and imaginary anomalous-dispersion scattering-factor correlation of Cromer and Liberman¹⁵ were included.

Electric Conductivity Measurements. The samples examined for dc conductivity studies (using the apparatus described previously⁹) were nearly hexagonal prisms, with all dimensions on the order of a few tenths of a millimeter. The small crystal size permitted only two probe conductivity measurements, though orientations both parallel and perpendicular to the hexagonal plane could be examined. Samples were mounted by pressure contact between two spring-loaded brass pins.

RESULTS AND DISCUSSION

The reaction of TTF with iodine in acetonitrile, followed by slow cooling, yields $\text{TTF} \cdot \text{I}_x$ phases of various stoichiometries (see Experimental Section for methodology). The small quantities of $\text{TTF} \cdot \text{I}_3$ crystals formed were mechanically separated from the other phases.

Description of the Structure. The final atomic coordinates and anisotropic temperature factors are given in Table I. A stereoscopic view of the unit cell contents is shown in Figure 1 and the I_3^- ion close contacts are illustrated in Figure 2. The crystal structure consists of integrated stacks of cofacial TTF^+ dimers in alternation with pairs of triiodide ions. The TTF^+ cation is distorted somewhat from planarity, with all sulfur atoms 0.01-0.03 Å below (i.e. toward the other molecule of the dimer) and all carbon atoms 0.0-0.03 Å above the least-squares best plane. The spacing between least-squares best planes for the TTF^+ ions within the dimer is 3.40(1) Å, but the S-S distances of 3.351(2) and 3.373(2) Å are somewhat shorter. The molecular packing in $\text{TTF} \cdot \text{I}_3$ is reminiscent of that communicated for $\text{TTF} \cdot \text{Br}$ (and isomorphous $\text{TTF} \cdot \text{Cl}$), also integral oxidation state salts.^{4i, j, 16} In these materials, integrated stacks of $(\text{TTF})_2^{+2}$ dimers and halide ions also occur. The interplanar spacing between members of the dimer appears to be somewhat larger in the present case (3.40(1) Å) than in $\text{TTF} \cdot \text{Br}$ (3.34 Å).^{4i, j, 16}

These interplanar spacings are considerably shorter than the TTF spacings of 3.55 (1) Å found in the segregated stack structures of TTF·I_{0.71} and TTF·I₂. The spacings in the present case are also shorter than in the eclipsed (TTF)₂⁺² dimers of (TTF)₂Ni(S₄C₄H₄) (here the S-S distance is given as 3.48 Å).¹⁷ The direct axis fractional components of the TTF⁺ plane normal in TTF·I₃ are (0.0679, -0.0099, 0.1166) which is approximately along the <102> direction. The TTF⁺ ions are almost exactly superimposed with a slight lateral offset of about 0.25 Å perpendicular to the long axis of the molecule.

The molecular structural parameters for TTF·I₃ are summarized in Table II. In Figure 3, the bond distances and angles within the tetrathiafulvalenium ion are illustrated. These indicate that the cation is rather symmetrical, even though this is not required by the crystallographic symmetry. A comparison of the TTF⁺ structural data with that of other TTF cations as well as with neutral TTF is set out in Table III. It can be seen that oxidation is accompanied by lengthening of the exocyclic double bond (a) and shortening of the contacts between the two carbon atoms involved in the exocyclic double bond and the sulfur atoms (b). The metrical parameters for TTF⁺ in the present study are experimentally indistinguishable from those in TTF·Br.¹⁶

The TTF·I₃ crystal structure also contains parallel, zig-zagging chains of triiodide ions. The arrangement of the triiodide ions is illustrated in Figure 2. The triiodide ion deviates slightly from

linearity with an I-I-I angle of $175.40(2)^\circ$. This slight bending is frequently observed in structures of triiodides (Table IV) and reflects the rather flat potential energy surface for molecular distortion.¹⁸ The fact that the terminal iodine atoms of the I_3^- ion are slightly displaced toward the positively charged $(TTF)_2^{+2}$ dimer can be explained on an electrostatic basis. The negative charge in I_3^- is localized principally on these two atoms.^{9a, 14} The slight asymmetry in the I-I distances, $2.908(1)$ and $2.953(1)$ Å, presumably also reflects the environment and ready deformability of the I_3^- ion. The I-S contacts are illustrated in Figure 2, and the closest distances are in the range $3.636(2) - 3.989(2)$ Å. These values are typical of the I-S contacts found in $TTF \cdot I_x$ systems. In the more closely packed $TTF \cdot I_{0.7}$ structure, the I-S contacts are as small as 3.53 Å.^{4h} As shown in Figure 2, the closest contact between proximate I_3^- ions is $4.335(1)$ Å.

Electrical Conductivity. The room temperature dc conductivities of two single crystal samples of $TTF \cdot I_3$ were measured parallel to the hexagonal plane and found to have values of $6 \times 10^{-9} \Omega^{-1} \text{ cm}^{-1}$ and $9 \times 10^{-10} \Omega^{-1} \text{ cm}^{-1}$. The dc conductivity of the latter sample was also measured perpendicular to the hexagonal plane. Here the geometry put the precise value of the conductivity beyond the limita-

tions of the instrumentation, although an upper limit of $9 \times 10^{-9} \Omega^{-1} \text{ cm}^{-1}$ was determined. Finally, a small polycrystalline sample was examined and found to have $\sigma = 8 \times 10^{-10} \Omega^{-1} \text{ cm}^{-1}$.

CONCLUSIONS

This work shows the high iodine phase of the $\text{TTF} \cdot \text{I}_x$ system $x = 3$, to be an integrated stack material with integral formal oxidation states, i.e. $\text{TTF}^+ \text{I}_3^-$. Not surprisingly, such a structure gives rise to high electrical resistivity. As in the case of the other known integral oxidation state tetrathiafulvalenium salts,^{4h, i} the structural motif in $\text{TTF} \cdot \text{I}_3$ consists of integrated stacks of alternating $(\text{TTF})_2^{+2}$ dimers and pairs of counter anions. Those factors which govern the stability of various possible crystal structures in TTF salts have been discussed at length.^{4h, i, 19, 20} It appears that the present structural result can be best rationalized in terms of the electrostatic destabilization with respect to the partially oxidized situation of an integral oxidation state (+I) segregated stack structure.^{4h, i, 19} In addition, the close interplanar separation in the $(\text{TTF})_2^{+2}$ suggests enhanced covalent bonding^{20, 21} between the cationic moieties in the integral oxidation state case.

ACKNOWLEDGMENTS

The chemical and physicochemical research at Northwestern University was generously supported by the Office of Naval Research, and by the NSF-MRL program through the Materials Research Center of

Northwestern University (grant DMR76-80847). The crystallographic studies at Oak Ridge National Laboratory were generously supported by the Division of Materials Sciences, U.S. Department of Energy, under contract W-7405-eng-26 with the Union Carbide Corporation. We also thank Mr. M. McClure for assistance with the conductivity measurements and Dr. S.J. La Placa of IBM Watson Laboratories for communicating his structural data on TTF·Br.

Supplementary Material Available: A listing of structure amplitude tables (21 pages). Ordering information is given on any current masthead page.

REFERENCES

- (1) a. Department of Chemistry and the Materials Research Center, Northwestern University.
- b. Visiting Scientist, Oak Ridge National Laboratory.
- c. Present address: Research Laboratories, Eastman Kodak Co., Kodak Park, Rochester, NY 14650.
- d. Chemistry Division, Oak Ridge National Laboratory.
- (2) Camille and Henry Dreyfus Teacher-Scholar.
- (3) a. Devreese, J. T.; Evrard, V. E.; Van Doren, V. E., Highly Conducting One-Dimensional Solids, Plenum Press, N.Y., 1979.
- b. Torrance, J. B. Accts. Chem. Res., 1979, 12, 79-86.
- c. Miller, J. S.; Epstein, A. J., eds., Synthesis and Properties of Low-Dimensional Materials, Ann. N.Y. Acad. Sci., 1978, 313.
- d. Keller, H. J., ed. Chemistry and Physics of One-Dimensional Metals, Plenum Press, New York, 1977.
- e. Miller, J. S.; Epstein, A. J. Prog. Inorg. Chem., 1976, 20, 1-1151.
- f. Keller, H. J., ed. Low Dimensional Cooperative Phenomena, Plenum Press, N.Y. 1975.
- g. Soos, Z. G.; Klein, D. J. in Molecular Associations, Foster, R., ed., Academic Press, N.Y., 1975, chapt. 1.
- (4) a. Warmack, R. J.; Callcott, T. A.; Watson, C. R. Phys. Rev. B. 1975, 12, 3336-3338.
- b. Somoano, R. B.; Gupta, A.; Hadek, V.; Datta, T.; Jones, R.; Herman, A. M. J. Chem. Phys., 1975, 63, 4970-4976.
- c. Johnson, C. K.; Watson, Jr., C. R.; Warmack, R. J. Abstr. Amer. Cryst. Assoc., 1975, 3, 19.

- d. Daly, J.J.; Sanz, F. Acta. Crystallogr. Sec. B., 1975, 31, 620-
 - e. LaPlaca, S.J.; Corfield, P.W.R.; Thomas, R.; Scott, B.A. Solid State Commun., 1975, 17, 635-638.
 - f. LaPlaca, S.J. Bull. Amer. Phys. Soc., 1975, 20, 496.
 - g. Johnson, C.K.; Watson, C.R., Jr.; Warmack, R.J. Chem. Div. Ann. Prog. Rep., Oak Ridge National Laboratory, 1976, 102-103.
 - h. Johnson, C.K.; Watson, C.R., Jr. J. Chem. Phys., 1976, 64, 2271-2286.
 - i. Scott, B.A.; LaPlaca, S.J.; Torrance, J.B.; Silverman, B.D.; Welber, B. J. Amer. Chem. Soc., 1977, 99, 6631-6639.
 - j. Scott, B.A.; LaPlaca, S.J.; Torrance, J.B.; Silverman, B.D.; Welber, B. in reference 3c, p. 369-376.
- (5) For ^{129}I Mössbauer studies see:
- a. Marks, T.J. in reference 3c, p. 594-616.
 - b. Teitelbaum, R.C.; Marks, T.J. manuscript in preparation.
- (6) Marks, T.J.; Teitelbaum, R.C.; McClure, M.S.; Kannewurf, C.R.; Johnson, C.K.; Ruby, S.L.; Bull Amer. Phys. Soc., 1979, 24, 233.
- (7) a. Resonance Raman studies indicate that the major polyiodide constituent is a slightly distorted triiodide.^{6, 7b}
- b. Teitelbaum, R.C.; Marks, T.J. unpublished results.
 - c. Johnson, C.K., manuscript in preparation.
- (8) For discussions of the structural chemistry of low-dimensional materials see:

- a. Kistenmacher, T.J. in reference 3c, p. 333-342.
 - b. Megtert, S.; Pouget, J. P.; Comes, R. in reference 3c, p. 234-243.
 - c. Stucky, G.D.; Schultz, A.J.; Williams, J. M. Ann. Rev. Mater. Sci., 1977, 7, 301-339.
 - d. Bespalov, B. P.; Titov, V.V. Russ. Chem. Rev., 1975, 44, 1091-1108.
 - e. Dahm, D.J.; Horn, P.; Johnson, G.R.; Miles, M.G.; Wilson, J.D. J. Cryst. Mol. Struct., 1975, 5, 27-34.
 - f. Herbstein, F.H. Perspect. Struct. Chem., 1971, IV, 166-395.
- (9) a. Cowie, M.A.; Gleizes, A.; Grynkewich, G.W.; Kalina, D.W.; McClure, M.S.; Scaringe, R. P.; Teitelbaum, R.C.; Ruby, S.L.; Ibers, J.A.; Kannewurf, C.R.; Marks, T.J. J. Amer. Chem. Soc., 1979, 101, 2921-2936.
- b. Brown, L.D.; Kalina, D.W.; McClure, M.S.; Ruby, S.L.; Schultz, S.; Ibers, J.A.; Kannewurf, C.R.; Marks, T.J. J. Amer. Chem. Soc., 1979, 101, 2937-2947.
- (10) a. Schramm, C J.; Stojakovic, D.R.; Hoffman, B.M.; Marks, T.J. Science, 1978, 200, 47-48.
- b. Petersen, J.L.; Schramm, C.S.; Stojakovic, D.R.; Hoffman, B.M.; Marks, T.J. J. Amer. Chem. Soc., 1977, 99, 286-288.
- c. Scaringe, R. P.; Schramm, C.J.; Stojakovic, D.R.; Hoffman, B.M.; Ibers, J.A.; Marks, T.J., submitted for publication.
- d. Stojakovic, D.R. Ph.D. Thesis, Northwestern University, August 1977.
- (11) Germain, G.; Main, P.; Woolfson, M.M. Acta. Crystallogr., Sect. A, 1971, 27, 368-376.
- (12) See paragraph at end of paper regarding supplementary material.

- (13) Ibers, J.A.; Hamilton, W.C., eds. International Tables for X-ray Crystallography, 1974, Vol. IV, Kynoch Press, Birmingham, England.
- (14) a. Potasek, M.J.; Debrunner, P.G.; Morrison, W.H., Jr.; Hendrickson, D.N. J. Chem. Phys., 1974, 70, 2203-2206.
- b. Datta, S.N.; Ewig, C.S.; Van Wazer, J.R. J. Mol. Struct., 1978, 48, 407-416.
- (15) Cromer, D.T.; Liberman, D. J. Chem. Phys., 1970, 53, 1891-1898.
- (16) S.J. LaPlaca, private communication
- (17) Kasper, J.S.; Interrante, L.V.; Secaur, C.A. J. Amer. Chem. Soc., 1975, 97, 890-891.
- (18) a. Brown, R.D.; Nunn, E.K. Austral. J. Chem., 1966, 19, 1567-1576.
- b. Migchelsen, T.; Vos, A. Acta Cryst., 1967, 22, 812-815.
- c. Rundle, R.E. Acta Cryst., 1961, 14, 585-589.
- (19) a. Torrance, J.B.; Silverman, B.D. Phys. Rev. B, 1977, 15, 788-801.
- b. Silverman, B.D. Phys. Rev. B, 1978, 17, 2482-2485.
- c. Epstein, A.J.; Lipari, N.O.; Sandman, D.J.; Nielsen, P. Phys. Rev. B, 1976, 13, 1569-1579.
- d. Metzger, R.M. in reference 3c, p. 145-164, and references therein.
- (20) a. Silverman, B.D. J. Chem. Phys., 1979, 70, 1614-1620.
- b. Salahub, D.R.; Messmer, R.P.; Herman, F. Phys. Rev. B, 1976, 13, 4252-4257.
- (21) Interrante, L.V.; Browall, K.W.; Hart, H.R., Jr.; Jacobs, I.S.; Watkins, G.D.; Wee, S.H. J. Amer. Chem. Soc., 1975, 97, 889-890.

Table 1
Fractional Atomic Coordinates and Anisotropic Thermal Parameters

atom	x	y	z	β_{12}	β_{22}	β_{33}	β_{12}	β_{13}	β_{23}
U(1)	.34364(5)	-.12731(2)	.62281(6)	.01029(6)	.00230(1)	.01948(10)	.00085(2)	.00253(6)	-.00117(3)
U(2)	.36909(4)	.02401(2)	.70257(5)	.00699(5)	.00205(1)	.01434(8)	.00016(2)	.00241(5)	.00072(2)
U(3)	.37473(5)	.17644(2)	.79679(7)	.01207(2)	.00180(1)	.02430(11)	-.00078(2)	.00441(7)	.00130(3)
S(1)	.2568(2)	.0726(8)	.1492(2)	.0077(2)	.00171(4)	.0188(3)	-.00062(7)	.0035(2)	-.00038(9)
S(2)	.0096(2)	.0611(8)	.3138(2)	.0095(2)	.00188(4)	.0130(3)	.00075(7)	.0036(2)	-.00029(8)
S(3)	-.0098(2)	-.1074(8)	.2256(2)	.0088(2)	.00178(4)	.0148(3)	-.00053(7)	.0032(2)	-.00029(8)
S(4)	.2390(2)	-.0942(8)	.0646(2)	.0082(2)	.00175(4)	.0161(3)	.00062(7)	.0034(2)	.00036(8)
C(1)	.1204(6)	-.0530(3)	.1738(7)	.0060(6)	.00162(14)	.0090(8)	.0005(2)	.0013(6)	-.00070(8)
C(2)	.1306(6)	.0188(3)	.2127(7)	.0056(6)	.00166(14)	.0090(9)	.0001(2)	.0007(6)	.0000(3)
C(3)	.2024(8)	.1492(3)	.2370(9)	.0123(10)	.00149(15)	.0199(13)	-.0008(3)	.0010(14)	-.0001(3)
C(4)	.0905(8)	.1434(3)	.3132(9)	.0157(11)	.00157(16)	.0161(12)	.0007(4)	.0024(10)	-.0009(4)
C(5)	.0529(8)	-.1848(3)	.1436(9)	.0108(9)	.00154(15)	.0198(14)	-.0005(3)	.0005(10)	.0010(4)
C(6)	.1653(8)	-.1783(3)	.0701(9)	.0123(9)	.00186(17)	.0177(13)	.0007(3)	.0014(10)	-.0001(4)
H(3)	.255(10)	.193(4)	.209(11)						
H(4)	.039(10)	.186(4)	.356(11)						
H(5)	-.006(10)	-.230(4)	.162(11)						
H(6)	.218(10)	-.218(4)	.013(11)						

Table II. Selected Distances and Angles in TTF·I₃

Bond Distances (Å)

I(1) - I(2)	2.907(1)	S(3) - C(5)	1.743(7)
I(2) - I(3)	2.953(1)	S(4) - C(1)	1.731(6)
S(1) - C(2)	1.715(6)	S(4) - C(6)	1.730(7)
S(1) - C(3)	1.718(7)	C(1) - C(2)	1.382(7)
S(2) - C(2)	1.718(6)	C(3) - C(4)	1.326(11)
S(2) - C(4)	1.724(7)	C(5) - C(6)	1.317(11)
S(3) - C(1)	1.713(6)		

Non-Bonded Contacts (Å)


I(1) - S(2)'	3.686(2)	I(3) - S(4)	3.870(2)
- S(4)'''	3.832(2)	I(1) - C(1)	3.898(5)
- S(1)''	3.911(2)	I(2) - C(2)	3.955(5)
I(2) - S(3)'	3.881(2)	I(3) - C(4)	3.933(7)
- S(2)'	3.882(2)	I(3) - C(6)	3.902(7)
- S(1)''	3.985(2)	S(1) - S(3)'''	3.351(2)
- S(4)''	3.946(2)	S(2) - S(4)'''	3.372(2)
- S(1)'''	3.959(2)	C(1) - C(2)'''	3.434(7)
- S(4)'''	3.989(2)	C(3) - C(5)'''	3.424(9)
I(3) - S(3)'	3.637(2)	C(4) - C(6)'''	3.439(10)
- S(1)'''	3.732(2)		

Bond Angles (deg)

I-I-I	175.39(2)	S(3) - C(1) - S(4)	115.1(2)
S(1) - C(2) - C(1)	122.1(4)	S(1) - C(2) - S(2)	115.7(3)
S(2) - C(2) - C(1)	122.1(4)	C(4) - C(3) - S(1)	116.6(5)
S(3) - C(1) - C(2)	123.3(4)	C(3) - C(4) - S(2)	118.1(5)
S(4) - C(1) - C(2)	121.5(4)	C(6) - C(5) - S(3)	117.0(5)
C(2) - S(1) - C(3)	95.2(3)	C(5) - C(6) - S(4)	117.4(5)
C(2) - S(2) - C(4)	94.2(3)		
C(1) - S(3) - C(5)	95.2(3)		
C(6) - S(4) - C(1)	95.1(3)		

Table III. Dimensions of TTF molecule averaged over assumed mmm molecular symmetry.

	$\frac{\text{TTF}^a}{295^\circ \text{K}}$	$\frac{\text{TTF-TCNQ}^b}{298^\circ \text{K}}$	$\frac{\text{TTF} \cdot \text{I}_2^c}{295^\circ \text{K}}$	$\frac{\text{TTF} \cdot \text{I}_3^d}{295^\circ \text{K}}$	$\frac{\text{TTFBr}^e}{295^\circ \text{K}}$
a	1.349(3)	1.369(4) Å	1.350 Å	1.382(7) Å	1.393 Å
b	1.757(2)	1.743(4)	1.732	1.719(8)	1.720
c	1.726(4)	1.736(5)	1.721	1.728(11)	1.724
d	1.314(3)	1.323(4)	1.336	1.322(11)	1.332
α	122.8(2)	122.6(3)	122.9	122.5(8)°	122.3°
β	114.5(2)	114.7(3)	114.3	115.4(4)	115.5
γ	94.4(2)	94.9(3)	95.7	94.9(5)	95.1
δ	118.3(4)	117.6(4)	117.2	117.3(6)	117.2

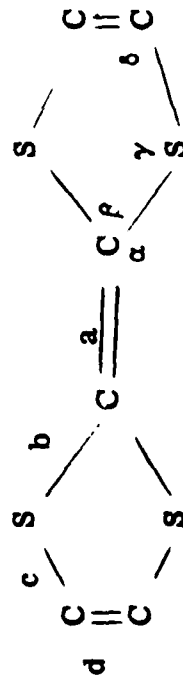

^a Phillips, T.E.; Kistenmacher, T.J.; Ferraris, Cowan, D.O. Chem. Comm. 1973, 14, 471-472.


^b Kistenmacher, T.J.; Phillips, T.E.; Cowan, D.O. Acta. Crystallogr. 1974, B30, 763-768.

^c Obtained by Fourier refinement and comparable standard errors are unavailable. Ref. 6c.

^d This work

^e Reference 16.

Table IV. Bond Angles and Distances in Triiodide Ions



	$\Theta(\text{deg})$	$a(\text{\AA})$	$b(\text{\AA})$
$\text{TTF} \cdot \text{I}_3^{\text{a}}$	175.39(2)	2.9533(8)	2.9078(7)
$\text{((C}_6\text{H}_5\text{))CONH}_2\text{)}_2\text{H}^+\text{I}_3^{\text{b}}$	177.2(5)	2.959(8)	2.900(8)
	176.5(4)	2.943(8)	2.921(8)
$(\text{C}_6\text{H}_5)_4\text{AsI}_3^{\text{c}}$	175.61(5)	2.920(2)	2.920(2)
CsI_3^{e}	177.9(1)	3.042(4)	2.840(4)
$\text{NH}_4\text{I}_3^{\text{d}}$	180.0(1)	3.113(4)	2.791(4)
$(\text{thiocarbamato})_2\text{CuI}_3^{\text{e}}$	176.5(3)	2.919(7)	2.899(7)
$(\text{phenacetin})_2 \cdot \text{H}^+\text{I}_3^- \cdot \text{I}_2^{\text{f}}$	180	2.907(1)	2.907(1)

^a This work.

^b This structure contains parallel chains of triiodide ions, with two types of I_3^- moieties; Reddy, J.M.; Knox, K.; Robin, M.B. J. Chem. Phys., **1964**, *40*, 1082-1089.

^c Runsink, J.; Swen-Walstra, S.; Migchelsen, T. Acta. Crystallogr., **Sect. B**, **1972**, *28*, 1331-1335.



^d Cheesman, G.H.; Finney, A.J.T., Acta. Crystallogr., **Sect. B**, **1970**, *26*, 904-906.


^e Wijnhoven, J.G.; Van den Hark, T.E.M.; Beurkeus, P.T. J. Cryst. Mol. Struct., **1972**, *2*, 189-196.

^f Herbstein, F.H.; Kapon, M. Nature (London), **1972**, *239*, 153-1954.


FIGURE CAPTIONS

- Figure 1. Stereoscopic view of the molecular packing of $\text{TTF} \cdot \text{I}_3$. The monoclinic \underline{b} axis is vertical.
- Figure 2. View of stacking within a sheet of $(\text{TTF})_2^{+2}$ dimers and triiodide ions in the ac plane. The zig-zagging triiodide chains along \underline{b} also are shown.
- Figure 3. Bond distances and angles in the TTF^+ ion. Probability ellipsoids (50%) and the numbering scheme are also shown.

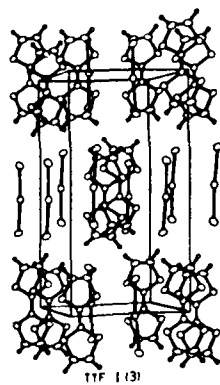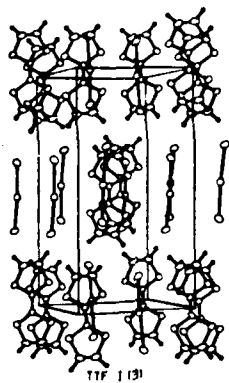

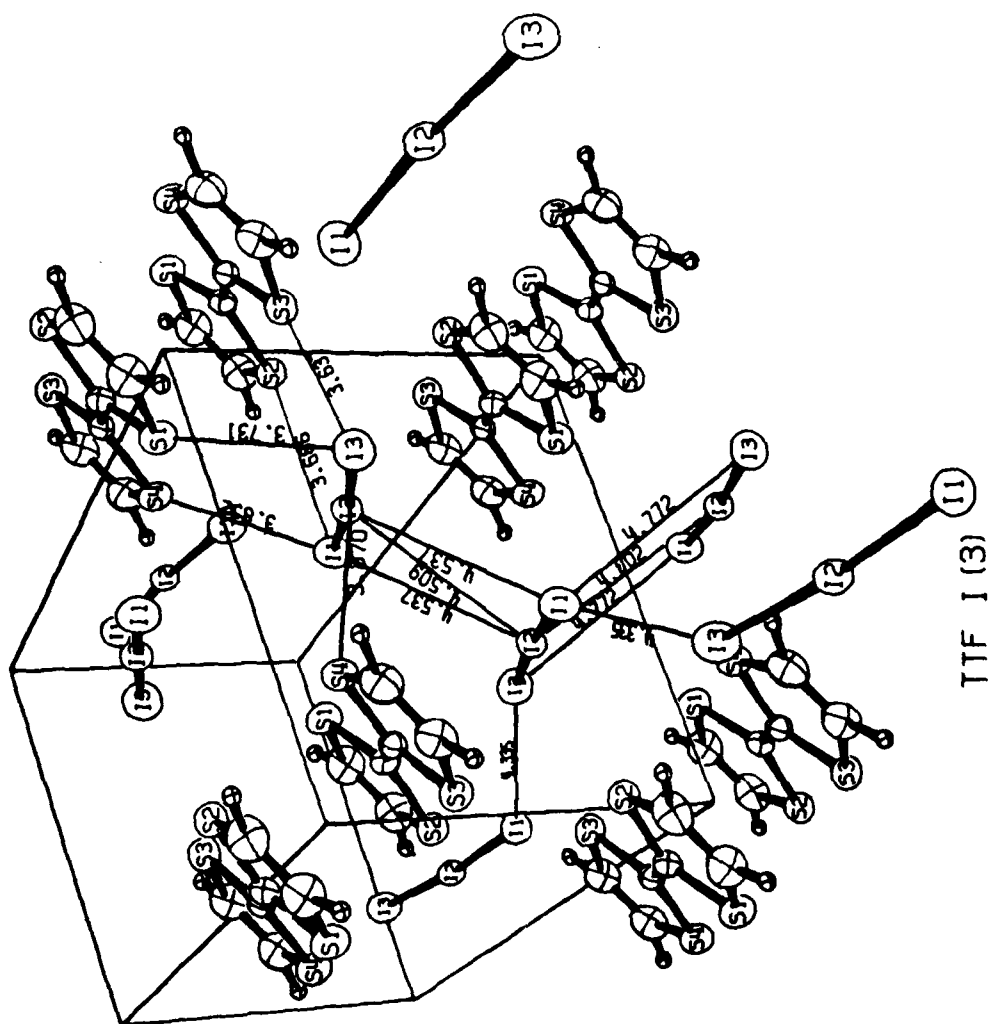

TTF I (3)

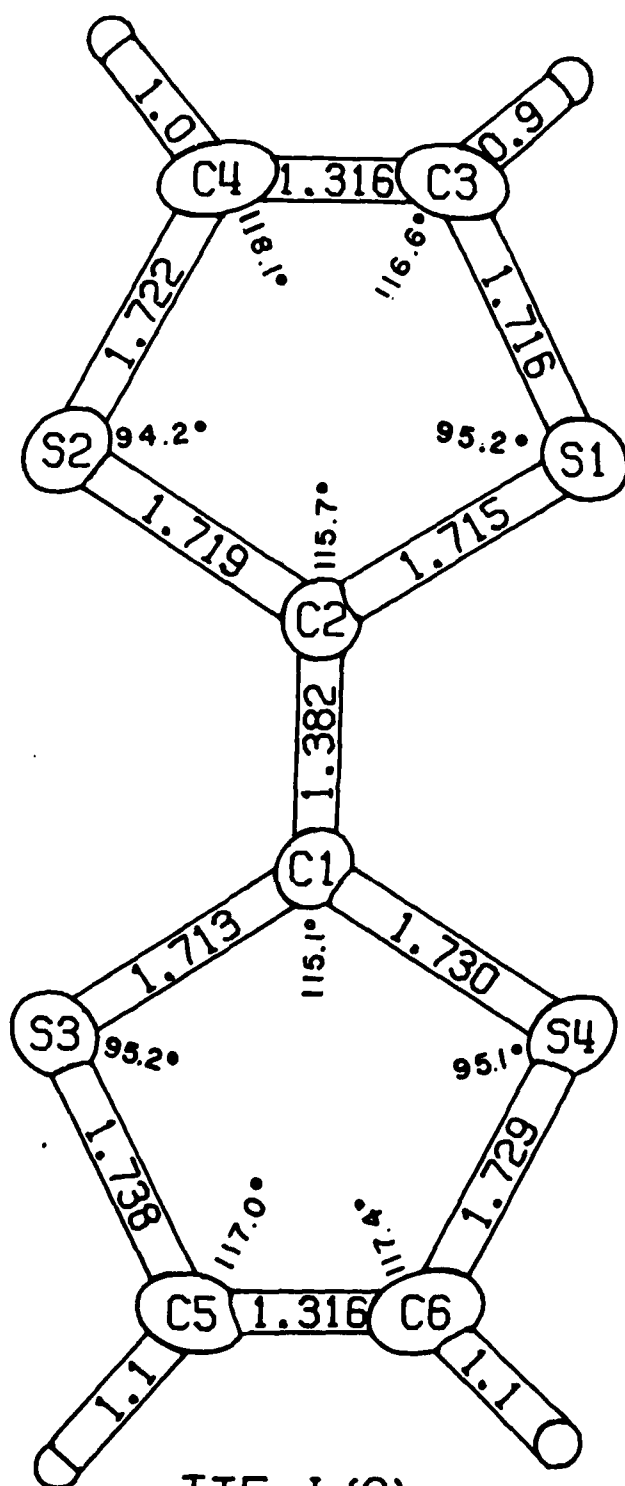

TTF I (3)

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Office of Naval Research Attn: Code 472 800 North Quincy Street Arlington, Virginia 22217	2	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 1211 Research Triangle Park, N.C. 27709	1
ONR Branch Office Attn: Dr. George Sandoz 536 S. Clark Street Chicago, Illinois 60605	1	Naval Ocean Systems Center Attn: Mr. Joe McCartney San Diego, California 92152	1
ONR Branch Office Attn: Scientific Dept. 715 Broadway New York, New York 10003	1	Naval Weapons Center Attn: Dr. A. B. Amster, Chemistry Division China Lake, California 93555	1
ONR Branch Office 1030 East Green Street Pasadena, California 91106	1	Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1
ONR Branch Office Attn: Dr. L. H. Peebles Building 114, Section D 666 Summer Street Boston, Massachusetts 02210	1	Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
Director, Naval Research Laboratory Attn: Code 6100 Washington, D.C. 20390	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
The Assistant Secretary of the Navy (R,E&S) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1	Office of Naval Research Attn: Dr. Richard S. Miller 800 N. Quincy Street Arlington, Virginia 22217	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Department of the Navy Washington, D.C. 20360	1	Naval Ship Research and Development Center Attn: Dr. G. Sosmajian, Applied Chemistry Division Annapolis, Maryland 21401	1
Defense Documentation Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Naval Ocean Systems Center Attn: Dr. S. Yamamoto, Marine Sciences Division San Diego, California 91232	1
Dr. Fred Saalfeld Chemistry Division Naval Research Laboratory Washington, D.C. 20375	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1

TECHNICAL REPORT DISTRIBUTION LIST, GEN

No.
Copies

Dr. Rudolph J. Marcus
Office of Naval Research
Scientific Liaison Group
American Embassy
APO San Francisco 96503

1

Mr. James Kelley
DTNSRDC Code 2803
Annapolis, Maryland 21402

1

TECHNICAL REPORT DISTRIBUTION LIST, 053

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Dr. R. N. Grimes University of Virginia Department of Chemistry Charlottesville, Virginia 22901	1	Dr. M. H. Chisholm Department of Chemistry Indiana University Bloomington, Indiana 47401	1
Dr. M. Tsutsui Texas A&M University Department of Chemistry College Station, Texas 77843	1	Dr. B. Foxman Brandeis University Department of Chemistry Waltham, Massachusetts 02154	1
Dr. M. F. Hawthorne University of California Department of Chemistry Los Angeles, California 90024	1	Dr. T. Marks Northwestern University Department of Chemistry Evanston, Illinois 60201	1
Dr. D. B. Brown University of Vermont Department of Chemistry Burlington, Vermont 05401	1	Dr. G. Geoffrey Pennsylvania State University Department of Chemistry University Park, Pennsylvania 16802	1
Dr. W. B. Fox Naval Research Laboratory Chemistry Division Code 6130 Washington, D.C. 20375	1	Dr. J. Zuckerman University of Oklahoma Department of Chemistry Norman, Oklahoma 73019	1
Dr. J. Adcock University of Tennessee Department of Chemistry Knoxville, Tennessee 37916	1	Professor O. T. Beachley Department of Chemistry State University of New York Buffalo, New York 14214	1
Dr. A. Cowley University of Texas Department of Chemistry Austin, Texas 78712	1	Professor P. S. Skell Department of Chemistry The Pennsylvania State University University Park, Pennsylvania 16802	1
Dr. W. Hatfield University of North Carolina Department of Chemistry Chapel Hill, North Carolina 27514	1	Professor K. M. Nicholas Department of Chemistry Boston College Chestnut Hill, Massachusetts 02167	1
Dr. D. Seyferth Massachusetts Institute of Technology Department of Chemistry Cambridge, Massachusetts 02139	1	Professor R. Neilson Department of Chemistry Texas Christian University Fort Worth, Texas 76129	1
Professor H. Abrahamson University of Oklahoma Department of Chemistry Norman, Oklahoma 73019	1	Professor M. Newcomb Texas A&M University Department of Chemistry College Station, Texas 77843	1